

## Lexan\* Resin 121R

Americas: COMMERCIAL

UL rated HB as of 10/97. 200 series recommended when V-2 rating required. Nonhalogenated. 17.5 MFR, for small, intricate parts. Internal mold release.

Property

TYPICAL PROPERTIES <sup>(1)</sup>			
Property	Value	Unit	Standard
<b>MECHANICAL</b>			
Tensile Stress, yld, Type I, 50 mm/min	62	MPa	ASTM D 638
Tensile Stress, brk, Type I, 50 mm/min	118	MPa	ASTM D 638
Tensile Strain, yld, Type I, 50 mm/min	7	%	ASTM D 638
Tensile Strain, brk, Type I, 50 mm/min	125	%	ASTM D 638
Flexural Stress, yld, 1.3 mm/min, 50 mm span	96	MPa	ASTM D 790
Flexural Modulus, 1.3 mm/min, 50 mm span	2340	MPa	ASTM D 790
Hardness, Rockwell M	70	-	ASTM D 785
Hardness, Rockwell R	118	-	ASTM D 785
Taber Abrasion, CS-17, 1 kg	10	mg/1000cy	ASTM D 1044
<b>IMPACT</b>			
Izod Impact, unnotched, 23°C	3204	J/m	ASTM D 4812
Izod Impact, notched, 23°C	694	J/m	ASTM D 256
Tensile Impact, Type "S"	546	kJ/m <sup>2</sup>	ASTM D 1822
Falling Dart Impact (D 3029), 23°C	169	J	ASTM D 3029
Instrumented Impact Energy @ peak, 23°C	62	J	ASTM D 3763
Izod Impact, unnotched 80*10*3 +23°C	NB	kJ/m <sup>2</sup>	ISO 180/1U
Izod Impact, unnotched 80*10*3 -30°C	NB	kJ/m <sup>2</sup>	ISO 180/1U
Izod Impact, notched 80*10*3 +23°C	65	kJ/m <sup>2</sup>	ISO 180/1A
Izod Impact, notched 80*10*3 -30°C	11	kJ/m <sup>2</sup>	ISO 180/1A
Charpy 23°C, V-notch Edgew 80*10*3 sp=62mm	65	kJ/m <sup>2</sup>	ISO 179/1eA
Charpy -30°C, V-notch Edgew 80*10*3 sp=62mm	12	kJ/m <sup>2</sup>	ISO 179/1eA
Charpy 23°C, Unnotch Edgew 80*10*3 sp=62mm	NB	kJ/m <sup>2</sup>	ISO 179/1eU
Charpy -30°C, Unnotch Edgew 80*10*3 sp=62mm	NB	kJ/m <sup>2</sup>	ISO 179/1eU
<b>THERMAL</b>			
Vicat Softening Temp, Rate B/50	154	°C	ASTM D 1525
HDT, 0.45 MPa, 6.4 mm, unannealed	137	°C	ASTM D 648
HDT, 1.82 MPa, 6.4 mm, unannealed	129	°C	ASTM D 648
CTE, -40°C to 95°C, flow	6.84E-05	1/°C	ASTM E 831
Specific Heat	1.25	J/g-°C	ASTM C 351
Thermal Conductivity	0.25	W/m-°C	ASTM C 177
Relative Temp Index, Elec	130	°C	UL 746B
Relative Temp Index, Mech w/impact	130	°C	UL 746B

You may also be interested in:

Enhanced Property Data Sheet

Improved UV	<a href="#">SLX1231T</a>	<a href="#">Additional Info</a>
Improved Ductility	<a href="#">EXL1112</a>	<a href="#">Additional Info</a>
Improved Ductility	<a href="#">EXL1112T</a>	<a href="#">Additional Info</a>

Improved HDT [XHT4141](#) [Additional Info](#)

Value Unit Standard

Improved HDT [4301](#) [Additional Info](#)

Medical Grade [HP2](#) [Additional Info](#)

Relative Temp Index, Mech w/o impact	130	°C	UL 746B
<b>PHYSICAL</b>	<b>Value</b>	<b>Unit</b>	<b>Standard</b>
Specific Gravity	1.2	-	ASTM D 792
Specific Volume	0.83	cm <sup>3</sup> /g	ASTM D 792
Density	1.19	g/cm <sup>3</sup>	ASTM D 792
Water Absorption, 24 hours	0.15	%	ASTM D 570
Water Absorption, equilibrium, 23C	0.35	%	ASTM D 570
Water Absorption, equilibrium, 100°C	0.58	%	ASTM D 570
Mold Shrinkage, flow, 3.2 mm	0.5 - 0.7	%	SABIC Method
Melt Flow Rate, 300°C/1.2 kgf	17.5	g/10 min	ASTM D 1238
<b>OPTICAL</b>	<b>Value</b>	<b>Unit</b>	<b>Standard</b>
Light Transmission	88	%	ASTM D 1003
Haze	1	%	ASTM D 1003
Refractive Index	1.586	-	ASTM D 542
<b>ELECTRICAL</b>	<b>Value</b>	<b>Unit</b>	<b>Standard</b>
Volume Resistivity	>1.E+17	Ohm-cm	ASTM D 257
Dielectric Strength, in air, 3.2 mm	14.9	kV/mm	ASTM D 149
Relative Permittivity, 50/60 Hz	3.17	-	ASTM D 150
Relative Permittivity, 1 MHz	2.96	-	ASTM D 150
Dissipation Factor, 50/60 Hz	0.0009	-	ASTM D 150
Dissipation Factor, 1 MHz	0.01	-	ASTM D 150
Hot Wire Ignition {PLC}	2	PLC Code	UL 746A
High Voltage Arc Track Rate {PLC}	2	PLC Code	UL 746A
High Ampere Arc Ign, surface {PLC}	1	PLC Code	UL 746A
Comparative Tracking Index (UL) {PLC}	2	PLC Code	UL 746A
<b>FLAME CHARACTERISTICS</b>	<b>Value</b>	<b>Unit</b>	<b>Standard</b>
UL Recognized, 94HB Flame Class Rating (3)	0.71	mm	UL 94
Radiant Panel Listing	YES	-	UL Tested
UV-light, water exposure/immersion	F2	-	UL 746C

Source GMD, last updated:01/04/2000

## Processing

Parameter	Value	Unit
<b>Injection Molding</b>		
Drying Temperature	120	°C
Drying Time	3 - 4	hrs
Drying Time (Cumulative)	48	hrs
Maximum Moisture Content	0.02	%
Melt Temperature	280 - 305	°C
Nozzle Temperature	275 - 300	°C
Front - Zone 3 Temperature	280 - 305	°C
Middle - Zone 2 Temperature	270 - 295	°C
Rear - Zone 1 Temperature	260 - 280	°C
Mold Temperature	70 - 95	°C
Back Pressure	0.3 - 0.7	MPa
Screw Speed	40 - 70	rpm
Shot to Cylinder Size	40 - 60	%
Vent Depth	0.025 - 0.076	mm

Source GMD, last updated:01/04/2000

• NOTE: Back Pressure, Screw Speed, Shot to Cylinder Size and Vent Depth are only mentioned as general guidelines. These may not apply or need adjustment in specific situations such as low shot sizes, thin wall molding and gas-assist molding.


## CALCULATED FLOW LENGTH INDICATION

Moldflow® Radial Flow Analysis

Lexan® 121R

Melt Temperature : 290°C

Mold Temperature : 90°C

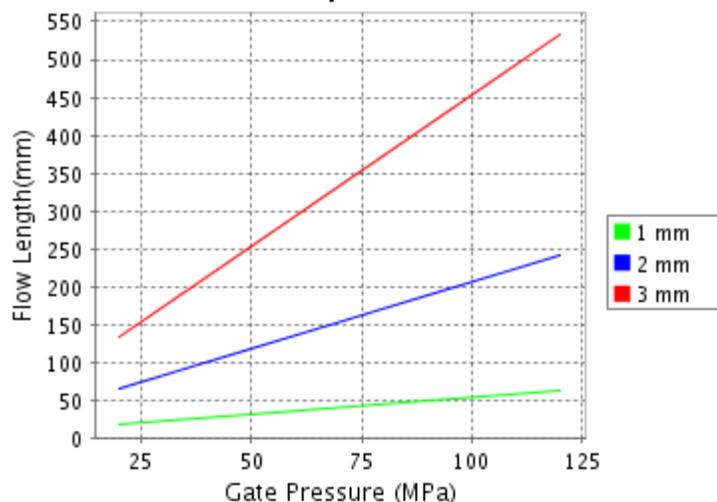

**Note: Technical support is recommended if Gate Pressure is greater than 80 MPa. Contact your local representative.**

® Moldflow is a registered trademark of the Moldflow Corporation.

THESE PROPERTY VALUES ARE NOT INTENDED FOR SPECIFICATION PURPOSES.

PLEASE CHECK WITH YOUR [\(LOCAL SALES OFFICE\)](#) FOR AVAILABILITY IN YOUR REGION

(1) Typical values only. Variations within normal tolerances are possible for various colors. All values are measured after at least 48 hours storage at 23°C/50% relative humidity. All properties, except the melt volume and melt flow rates, are measured on injection molded samples. All samples tested under ISO test standards are prepared according to ISO 294.

(2) Only typical data for selection purposes. Not to be used for part or tool design.

(3) This rating is not intended to reflect hazards presented by this or any other material under actual fire conditions.

(4) Internal measurements according to UL standards.

**Disclaimer :** THE MATERIALS AND PRODUCTS OF THE BUSINESSES MAKING UP THE SABIC INNOVATIVE PLASTICS COMPANY, ITS SUBSIDIARIES AND AFFILIATES ("SABIC IP"), ARE SOLD SUBJECT TO SABIC IP' S STANDARD CONDITIONS OF SALE, WHICH ARE INCLUDED IN THE APPLICABLE DISTRIBUTOR OR OTHER SALES AGREEMENT, PRINTED ON THE BACK OF ORDER ACKNOWLEDGMENTS AND INVOICES, AND AVAILABLE UPON REQUEST. ALTHOUGH ANY INFORMATION, RECOMMENDATIONS, OR ADVICE CONTAINED HEREIN IS GIVEN IN GOOD FAITH, SABIC IP MAKES NO WARRANTY OR GUARANTEE, EXPRESS OR IMPLIED, (I) THAT THE RESULTS DESCRIBED HEREIN WILL BE OBTAINED UNDER END-USE CONDITIONS, OR (II) AS TO THE EFFECTIVENESS OR SAFETY OF ANY DESIGN INCORPORATING SABIC IP MATERIALS, PRODUCTS, RECOMMENDATIONS OR ADVICE. EXCEPT AS PROVIDED IN SABIC IP' S STANDARD CONDITIONS OF SALE, SABIC IP AND ITS REPRESENTATIVES SHALL IN NO EVENT BE RESPONSIBLE FOR ANY LOSS RESULTING FROM ANY USE OF ITS MATERIALS OR PRODUCTS DESCRIBED HEREIN. Each user bears full responsibility for making its own determination as to the suitability of SABIC IP' s materials, products, recommendations, or advice for its own particular use. Each user must identify and perform all tests and analyses necessary to assure that its finished parts incorporating SABIC IP materials or products will be safe and suitable for use under end-use conditions. Nothing in this or any other document, nor any oral recommendation or advice, shall be deemed to alter, vary, supersede, or waive any provision of SABIC IP' s Standard Conditions of Sale or this Disclaimer, unless any such modification is specifically agreed to in a writing signed by SABIC IP. No statement contained herein concerning a possible or suggested use of any material, product or design is intended, or should be construed, to grant any license under any patent or other intellectual property right of SABIC Innovative Plastics Company or any of its subsidiaries or affiliates covering such use or design, or as a recommendation for the use of such material, product or design in the infringement of any patent or other intellectual property right

\* Lexan is a trademark of the SABIC Innovative Plastics Company

